

The Structural and Optical Properties of Perovskite Thin Films

Emine Guneri

Education Faculty, Erciyes University, Kayseri, Türkiye

Nilgun Kalaycioglu Ozpozan

Chemistry Department, Science Faculty, Erciyes,
University, Kayseri, Türkiye

Abstract

Perovskite materials have many interesting properties such as modulation of the optical band gap and the properties of quantum wells. In addition, they have a stable structure. For these reasons, perovskites have attractive properties for optoelectronic devices. Additionally, the structural and optical properties can be changed by means of different halide atoms doped into materials. In this study, the effect of iodine on the structural, and optical properties of perovskite thin films was investigated. KCaCl_2I and KCaCl_3 perovskite were prepared by chemical bath deposition on a glass substrate. The crystal structures of the films were determined by X-ray diffraction. X-Ray Diffraction (XRD) analysis revealed that the films had a crystalline structure. In addition, KCaCl_2I perovskite thin film has better crystalline than KCaCl_3 perovskite thin films. Linear optical parameters were determined using transmittance and absorbance measurements. And then, the optical band gap values, extinction coefficient, refractive index, and dielectric constants were determined as linear optical properties. It was understood that these properties were affected by iodine.

Keywords: perovskite, thin films, chemical bath deposition, optical properties, structural properties.

Introduction

A perovskite structure has the form ABX_3 , where A, and B are cations, and X is the anion (Wiley, et al. 2019; Korkmaz and Ozpozan-Kalaycioglu, 2012). Perovskites can have interesting a lot of properties because of the molecules in their structure (Kangning, et al. 1998). Therefore, studies on perovskite structures, in other words, perovskite thin films have increased in the last few years to improve the performance of devices such as optoelectronic devices. At end of the 19th century, perovskite

structures were formed in an aqueous solution by researchers (Mitzi, 1999; Soto-Montero, et al. 2020). However, these structures contained lead which is so dangerous for the environment (Katsanoulas, 1999). Hence, the research groups have tried to find materials that can be not dangerous to environmental and human health (Daskeviciute-Geguziene, et al. 2022).

Different deposition techniques such as ink-jet printing (Xie, 2018), co-evaporation (Park, 2019), and spin coating (Fong, 2021) have been used to form perovskite thin films.


In this work, the chemical bath deposition technique was used to obtain the perovskite thin films. The technique involves controlled precipitation of a solution of the compound on the substrate. With this technique, the structural and optical properties of the film can be changed by variables, such as solution temperature and precursor concentration. In the CBD method, a film can be formed on any substrate (Güneri, 2019). The aim of this study is to obtain KCaCl_2I and KCaCl_3 perovskite thin films using the CBD technique. Additionally, it is to show how iodine affects the structural and optical properties of perovskite thin films.

Experimental Details

The chemicals calcium chloride (CaCl_2 , Sigma Aldrich 99%), potassium iodide (KI, Sigma Aldrich 99%), dimethyl sulfoxide (DMSO), and dimethylformamide (DMF) were used in this study. The deposition of perovskite films was carried out using chemical bath deposition (CBD). Prior to the deposition of the thin films by CBD, the glass substrates were cleaned with detergent, deionized water, acetone, ethanol, isopropyl alcohol, and deionized water, respectively. To obtain KCaCl_2I perovskite thin films, CaCl_2 , KI, DMSO, and DMF were used in the bath. First of all, the stoichiometric ratio with CaCl_2 and KI was separately mixed in DMSO: DMF (3:7). The solvent mixture DMSO: DMF was used to boost the morphology control. To obtain a clear and homogenous solution, these mixes were continuously blended at room temperature for 24 hours. After obtaining homogenous solutions, the solutions were poured into the beaker, where the substrate cleaned was put. The deposition temperature and time were fixed at room temperature and 48h, respectively, to fabricate the film. The chemical reaction of the composition is given as follows:



To obtain KCaCl_3 perovskite thin films, KCaCl_2 , KCl, DMSO, and DMF, were used in the bath. The aforementioned process was repeated for KCaCl_2I perovskite thin film as well. The chemical reaction of the composition is given as follows:



The phase and orientation of the films were determined by XRD using a Panalytical Empyrean Model diffractometer. SHIMADZU & UV-2700 spectrophotometer were

used to determine the optical properties of films. All measurements were made at room temperature.

Results and Discussion

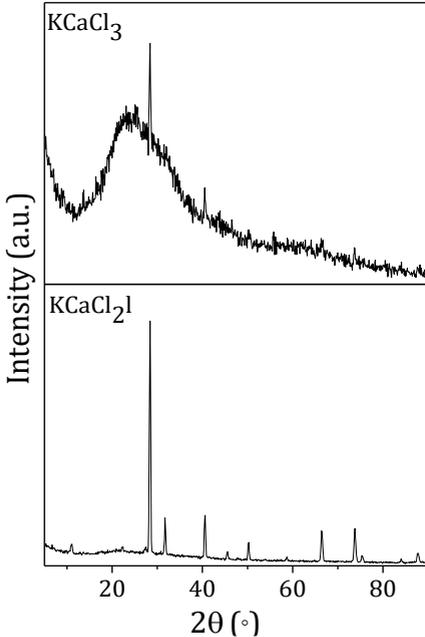


Fig. 1. XRD diffractograms pattern of KCaCl_2I perovskite thin film and KCaCl_3 perovskite thin film.

Fig.1 shows the XRD diffractograms of $\text{KCaCl}_2\text{I}/\text{glass}$ and $\text{KCaCl}_3/\text{glass}$, which have crystalline structures. The XRD diffractogram of KCaCl_2I perovskite thin film has four strong diffraction peaks, which are located at the angles 2θ : 28.39° , 40.56° , 66.4639° , and 73.7692° . These peaks didn't index the other materials. In this context, the new perovskite structure was fabricated in this work. The XRD diffractogram of KCaCl_3 perovskite thin film has a background due to dirtiness on the glass. Furthermore, there are just two peaks in its spectrum at the angles 2θ : 28.29° , and 40.29°

Fig. 2 shows the transmission, reflection, and absorption spectra of the KCaCl_2I and KCaCl_3 perovskite thin films. The transmission ratio of the KCaCl_2I perovskite thin film was lower than that of the KCaCl_3 perovskite thin film despite depositing time the same. There can be a lot of reasons. One of them is deposition velocity. The deposition velocity of the KCaCl_2I perovskite thin film can be faster than that of the KCaCl_3 perovskite thin film. When the refractive spectrum of both films was investigated, the refractive spectrum of KCaCl_2I perovskite thin films is higher than that of the KCaCl_3 perovskite thin film (Fig. 2). The origin of this difference can be iodine. The KCaCl_2I perovskite thin films have two maximum absorption peaks at 307 nm and 362 nm. These values show that there are two transmissions in the films. One of them can be

connected from the lower valence band (VB2) to the minimum conduction band (CB), and the other can be fatigued to the transition from the higher valence band (VB1) to the CB (Al-Asbahi, et al. 2020). The KCaCl_3 perovskite thin film absorbed most light below 350 nm.

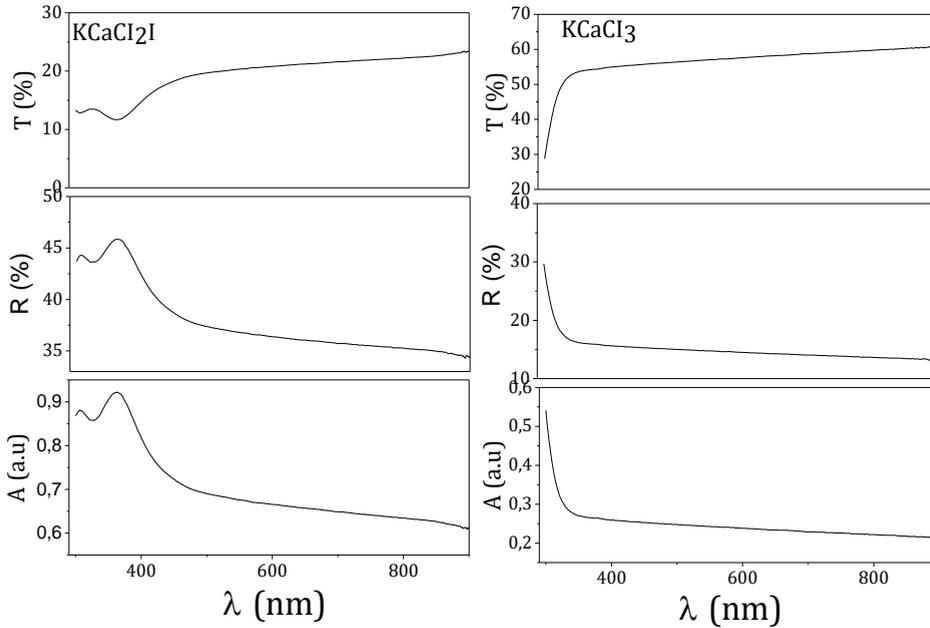


Fig. 2 The transmission, reflection, and absorption spectra of the KCaCl_2I and KCaCl_3 perovskite thin films.

The values of the direct energy band gaps of perovskite thin films were estimated from the Tauc plot of the absorption spectrum (Tauc, 1974). As seen in Fig. 3, the band gap values of the KCaCl_2I perovskite thin film are 2.45 eV (VB1 \rightarrow CB) and 2.65 eV (VB2 \rightarrow CB) while that of the KCaCl_3 perovskite thin film is 3.85 eV. These band gap values show that these films can be used as a window layer of a solar cell (Sharmin, et al. 2019).

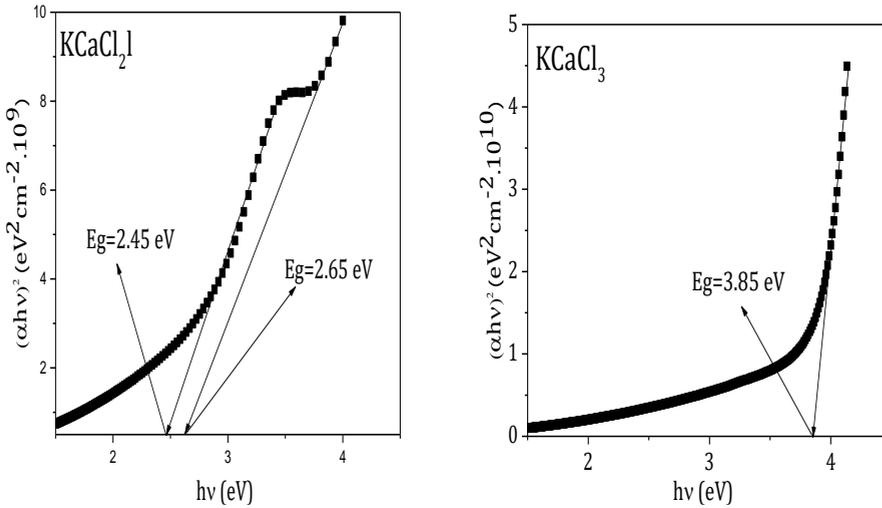


Fig. 3 $(\alpha h\nu)^2$ versus photon energy for the KCaCl₂I and KCaCl₃ perovskite thin films.

The refractive index and extinction coefficient of the films were determined using equations (Benramdane, et al. 1997). The non-linear dependence of the refractive index (n) and extinction coefficient (k) on the wavelength at room temperature can be seen in Fig. 4. Fig. 4 shows that KCaCl₂I and KCaCl₃ have different behavior for both parameters. The extinction coefficient of KCaCl₂I perovskite thin film increased from 425 nm. The refractive index of this film has also a reverse situation after 362 nm. The extinction coefficient of KCaCl₃ perovskite thin films increased from 325 nm. Additionally, the refractive index of KCaCl₃ perovskite thin films is almost constant and approximately 2.24–2.18. These values show that this film can be used for antireflection coating (Al-Asbahi, 2020).

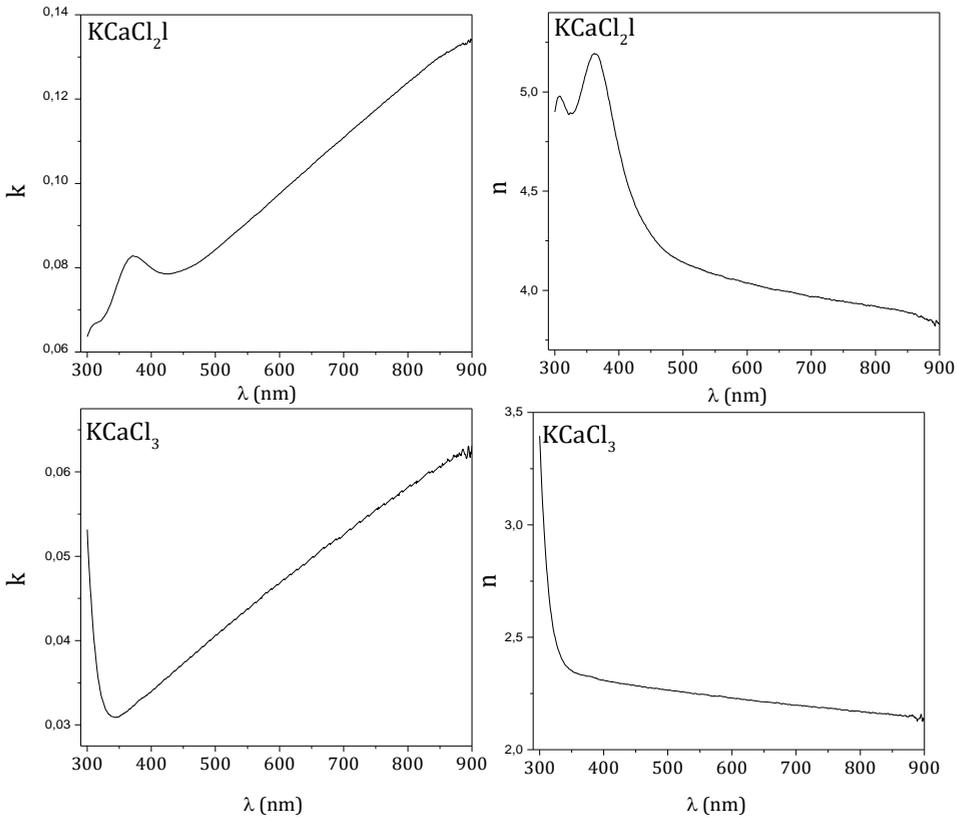


Fig. 4 The refractive index and extinction coefficient on wavelength in KCaCl_2I and KCaCl_3 perovskite films.

The real and imaginary parts of the dielectric constant of the films were calculated using the equations (Hodgson, 1970). According to Fig. 5, while the real and imaginary parts of the dielectric constant for KCaCl_2I perovskite films were found to be 16.23 and 0.78 at 600 nm, respectively, the real and imaginary parts of the dielectric constant for KCaCl_3 perovskite films were determined to be 4.99 and 20.21 at 600 nm, respectively.

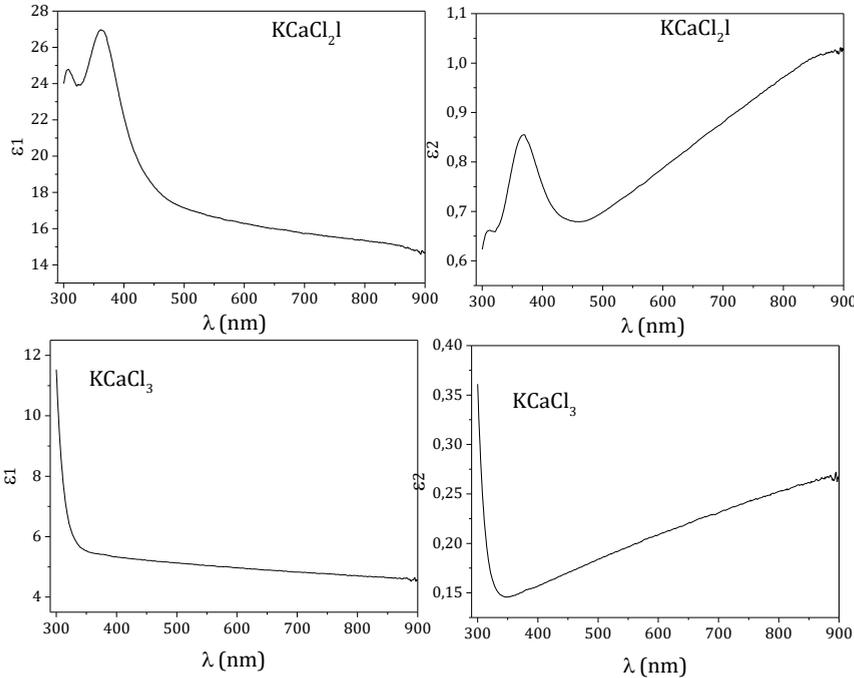


Fig. 5 The dependence of dielectric constants on wavelength in KCaCl_2I and KCaCl_3 perovskite films.

Conclusions

In this study, we successfully obtained KCaCl_2I and KCaCl_3 perovskite films via the CBD technique and compared the effect of iodine on the structural and optical properties of films by using characterization methods. According to XRD patterns, KCaCl_2I perovskite films have better crystalline structures than KCaCl_3 perovskite films. The band gap values of the KCaCl_2I perovskite thin film are 2.45 eV and 2.65 eV. The band gap value of the KCaCl_3 perovskite thin film is 3.85 eV. These band gap values show that both films can be used as a window layer of a solar cell. However, the KCaCl_3 perovskite thin film can be a better performance than the KCaCl_2I perovskite thin film as a window layer. To understand the effect of iodine on the properties of thin films, we plan to fabricate new films which will include different perovskite. Additionally, we will try using water instead of DMF: DMFO for green chemistry. In addition to all these, obtaining new perovskites using the solid state method and their differences can be investigated.

Acknowledgments

This work was fully supported by Erciyes University Scientific Research Projects Coordination Unit under the project numbers FBA-2022-11988. The authors wish to thank to Erciyes University.

References

- [1] Al-Asbahi, B., Qaid, S., Hezam, M., Bedja, I., Ghaithan, H., Aldwayyan, A. (2020). Effect of deposition method on the structural and optical properties of $\text{CH}_3\text{NH}_3\text{PbI}_3$ perovskite thin films. *Optical Materials*, 103,109836,
- [2] <https://doi.org/10.1016/j.optmat.2020.109836>.
- [3] Benramdane, N., Murad, W., Misco, R., Ziane, M., Kebbab, Z. (1997). A chemical method for the preparation of thin films of CdO and ZnO. *Mater. Chem. Phys.*, 48, 119, [https://doi.org/10.1016/S0254-0584\(97\)80104-6](https://doi.org/10.1016/S0254-0584(97)80104-6).
- [4] Daskeviciute-Geguziene, S., Zhang, Y., Rakstys, K. et al. (2022). Green-Chemistry-Inspired Synthesis of Cyclobutane-Based Hole-Selective Materials for Highly Efficient Perovskite Solar Cells and Modules. *Chem. Int. Ed.* 61, e202113207.
- [5] Fong, P. W. K., and Li, G. (2021). The Challenge of Ambient Air-Processed Organometallic Halide Perovskite: Technology Transfer From Spin Coating to Meniscus Blade Coating of Perovskite Thin Films. *Frontiers in Materials*, 8, 635224.
- [6] Hodgson, J. (1970). *Optical Absorption and Dispersion in Solids*. Chapman and hall LTD.
- [7] Kangning L., David B. Mitzi, and Michael T. Prikas. (1998). Synthesis and Characterization of Organic-Inorganic Perovskite Thin Films Prepared Using a Versatile Two-Step Dipping Technique. *Chemistry of Materials* 10 (1), 403-411. DOI: 10.1021/cm970568f
- [8] Katsanoulas, K., Papaioannou, A., Fraidakis, O. and Michaloudis, D. (1999). Undiagnosed central anticholinergic syndrome may lead to dangerous complications. *European Journal of Anaesthesiology*, 16(11), 803-809. doi:10.1046/j.1365-2346.1999.00583.x
- [9] Korkmaz, E., Ozpazan-Kalaycioglu, N. (2012). Synthesis and luminescence properties of $\text{BaTiO}_3\text{:RE}$ (RE = Gd^{3+} , Dy^{3+} , Tb^{3+} , Lu^{3+}) phosphors. *Bull Mater Sci* 35, 1011-1017 <https://doi.org/10.1007/s12034-012-0394-3>.
- [10] Güneri, E. (2019). The Role of Au Doping on the Structural and Optical Properties of Cu_2O Films. *Journal of Nano Research*, 58, 49-67.
- [11] <https://doi.org/10.4028/www.scientific.net/JNanoR.58.49>
- [12] Mitzi, D. (1999). *Synthesis, Structure, and Properties of Organic-Inorganic Perovskites and Related Materials* John Wiley and Sons Ltd.
- [13] Park, CG., Choi, WG., Na, S. et al. (2019). All-Inorganic Perovskite CsPbI_2Br Through Co-evaporation for Planar Heterojunction Solar Cells. *Electron. Mater. Lett.* 15, 56-60 <https://doi.org/10.1007/s13391-018-0095-1>

- [14] Sharmin, A., Tabassum, S., Bashar, M.S. Mahmood, Z. (2019). Depositions and characterization of sol-gel processed Al-doped ZnO (AZO) as transparent conducting oxide (TCO) for solar cell application. *J Theor Appl Phys* 13, 123–132. <https://doi.org/10.1007/s40094-019-0329-0>
- [15] Soto-Montero, T., Soltanpoor, W. and Morales-Masisa, M. (2020). Pressing challenges of halide perovskite thin film growth featured. *APL Materials* 8, 110903. <https://doi.org/10.1063/5.0027573>
- [16] Tauc, J. (1974) *Amorphous and liquid semiconductors*, Plenum Press, 171.
- [17] Wiley A. Dunlap-Shohl, Yuanyuan Zhou, Nitin P. Padture, and David B. Mitzi. (2019). Synthetic Approaches for Halide Perovskite Thin Films. *Chemical Reviews*, 119(5), 3193-3295
- [18] <https://doi.org/10.1021/acs.chemrev.8b00318>
- [19] Xie, M., Lu, H., Zhang, L., Wang, J., Luo, Q., Lin, J., Ba, L., Liu, H., Shen, W., Shi, L. and Ma, C.-Q. (2018). Fully Solution-Processed Semi-Transparent Perovskite Solar Cells With Ink-Jet Printed Silver Nanowires. *Top Electrode. Sol. RRL*, 2, 1700184. <https://doi.org/10.1002/solr.201700184>